

Al-Imam Muhammad Ibn Saud Islamic University
College of Science
Department of Chemistry

A Novel Approach for Dyeing Process of Wool Fabric with azoic dyes: Process Development and Optimization

A graduation research project
submitted to the Department of Chemistry in partial fulfillment of the requirements for the
completion of the degree of Bachelor of Science in Chemistry

By
Fahad Mohammed AL.Qhtani

Under supervision
of
Dr. Naoufel Ben Hamadi

Second Semester, May 2015

10-5-2015

21-7-1436



Acknowledgment

First of all thanks to ALLAH Almighty who gave me the strength and will to do this modest work. I would like to express my deep thanks and appreciation to those who encouraged me to make this thesis possible :

To my supervisions:

Dr. Naoufel Ben Hamadi whose sharp observations helped me through the obstacles of this work. I strongly appreciate his professional guidance , gracious time , encouragements and valuable remarks

To the chemistry Department , Faculty members at Al-Imam Muhammad ibn Saud Islamic University :

My deep thanks and gratitude for all the faculty members of the chemistry department For their fruitful contribution in the proposal especially professor, Kamal Taha, Profesor AbdelRahman EL.Gazzar , Profesor Magdi Zaki

To my family:

My whole hearted thanks and gratefulness goes to my parents who stood by me with their kind and valuable words of encouragment and advise,

Thank you and god bless all ...

CONTENTES

Acknowledgment	I
List of Tables	II
List of Figures	III
Abstract	IV
Chapter 1	
REVIEW OF LITERATURE	1
1.0 Introduction.....	3
2.0 DYES.....	4
2.1 Dye definition	4
2.2 Classification of dyes	5
2.3. Specific interest to azo dyes	6
2.4. Classification of azo dyes.....	8
2.4.1.Cationic or basic azo dyes	8
2.4.2 Anionic or acid azo dyes.....	8
2.5.3. Direct azo dyes.....	8
2.4.4. Reactive azo dyes	8
2.5.5. Mordant azo dyes.....	9
3.0 DYEING.....	9
3.1. Definition.....	9
4.0 WOOL	9
4.1. Structure and chemical composition of wool fibre.....	9
4.2. Chemical properties of wool fibre	11
4.2.1. Effect of acids.....	11
4.2.2. Effect of alkali	11

4.2.3. Effect of bleach	11
5.0 International Commission on Illumination: Color Systems	12
5.1. CIELAB (L*a*b*).....	12
5.2. CIELCH (L*C*h°)	12
5.3. Three-dimensional color system.....	13
5.3.1. Hue.....	13
5.3.2. Chroma	14
5.3.3. Lightness.....	14
Chapter 2	
1. Materials	16
1.1. Chemicals.....	16
1.2. Proton NMR Spectrometer.....	16
1.3. Infrared spectrometer	16
1.4. Wool fabrics.....	16
1.5. Dyeing materials.....	16
1.6. Equipement of Colour strength and colour depth measurements.....	17
1.7. Equipementof Rubbing Fastness test.....	18
1.8. Equipement of washing Fastness test.....	18
1.9. Equipement of testing the light Fastness propriety	19
2. Methods	19
2.1. Synthesis of azo dye	19
2.2. Wool pre-treatment	20
2.3. Dyeing procedure	20
2.4. Colour fastness test.....	20

Chapter 3

1.0 Synthesis and ¹H NMR study of azo dye 3	23
1.1. Structural study of azo dyes 3	23
2.0 Dyeing of wool fabrics with azo dye.....	24
2.1. Effect of azo dye concentration on the dyeing of wool fabrics	24
2.2. Effect of pH on the dyeing of wool fabrics	25
2.3. Effect of dyeing temperature	26
3.0 Colorimetric analysis of the dyed fabric.....	27
4.0 Fastness properties of the dye on wool fabrics	27

Chapter 4

4.0 CONCLUSION.....	27
---------------------	----

Chapter 5

5.0 REFERENCES.....	28
---------------------	----

Chapter 6

6.0 ABSTRACT (ARABIC).....	30
----------------------------	----

List of Tables

Table 1.1. Constitution (chemical) classes of dyes recognized in the <i>Colour Index</i>	7
Table 3.1. Color values of azo dye on wool: Effect of concentration	
Dyeing conditions: pH 3, 30 min, 60 °C	28
Table 3.2. Color values of azo dye on wool: Effect of pH	
Dyeing conditions: C 0.5, 30 min 60 °C.....	28
Table 3.3 Color values of azo dye on wool: Effect of dyeing temperature	
Dyeing conditions: C 0.5, 30 min	30
Table 3.4. Fastness properties of acid azo dye on wool fabric.....	30

List of Figures

Figure 1.2 – Cross-section diagram of a merino wool fibre showing the structure at progressive magnifications.....	12
Figure 1.3. Hue	16
Figure 1.4. Chromaticity	17
Figure 1.5. Three-dimensional color system depicting lightness	17
Figure 2.1 : Montage of preliminary dyeing experiments.....	20
Figure 2.2: AHIBA nuance Top speed II	20
Figure 2.3 : SF 300 spectrophotometer.....	21
Figure 2.4 : Crockmeter.....	21
Figure 2.5 : Autowash machine	22
Figure 2.6 : Suntest SPC Plus ATLAS	22
Figure 3.1 IR spectra of azo dye 3.....	26
Figure 3.2. ¹ H NMR spectra of azo dye 3.....	27

Abstract

New azo dye was synthesized from aromatic amines containing and 1-amino-4-methylnaphthalen-2-ol by diazotization and coupling reaction. This dye was characterized by FTIR and ^1H NMR analysis. The dyeing assessment of the synthesized dye was evaluated on wool. The dyed fiber show good light fastness and very good washing and rub fastness properties. Spectral properties and colorimetric data (L^* , a^* , b^* , C^* , h^* , K/S) have been investigated.

1.0 LITERATURE REVIEW

General Introduction

The textile industry is one among the rapidly growing industries worldwide. Textile industry utilizes enormous amounts of synthetic dyes. The industrial base greatly expanded in the Kingdom including all activities, among them are paper industry and paper products whose number increased by 18%. Textile is one of the developing sectors in Kingdom. Indeed, during the last five years, the textile factories increased from 19 to 28 factories.

Synthetic azo dyes are extensively used in textile dyeing, paper printing, color photography, pharmaceutical, food, cosmetics and other industries [1,2]. Among them the textile industry is a major consumer. These dyes have characteristically good tinctorial strength as well as stability. Azo dyes produce bright, high-intensity colors, have fair to good fastness properties, are economical to produce and account for more than half of all commercial dyes used. They have found wide application in dyeing of protein fibers such as wool, angora, cashmere, and silk, [3]. They attach to wool fibers via electrostatic linkages between the cationic, protonated amino end groups of wool (NH_3^+) and the anionic sulphonate groups of the dye (Dye-O^-) [4].

Azo compounds have also found their way into high-technology areas, such as colorants for liquid-crystalline materials and photoconductors for photoreceptors in copiers and laser printers [5].

Acid azo dyes containing aromatic heterocyclic moiety have been investigated due to their wide applications [6]. The use of heterocyclic diazo or coupling component has made the production of colorants having brilliant color and chromophoric strength [7].

In the same way, we have developed this work to synthesis a novel mono azo dyes and to investigate its application in textile dyeing. Moreover, spectral properties and colorimetric properties (L^* , a^* , b^* , C^* , H^* , K/S) have been also studied in detail.

In agreement with the aims defined for the present project, the manuscript began with a general introduction, and then a bibliographic revision is made, in chapter 1, concerning the most relevant topics related to the use of azo dye for wool dyeing.

The second part contains the general methods and the materials utilized in the scope of this project.

The third part presents a general discussion, the major results, conclusions and gives some perspectives for continuing the work in this research field.

1. Introduction

Color and its various uses come over the horizon from pre-historical period by all cultural groups and on all major land masses. The ancestors of man must have noticed (perhaps with or without understanding) the abundance of multitude of colors worn by nature. Certainly it would have been fascinating to them. Every civilization has its myth and association with color.

“Colorant” is used as a name for materials such as dyes and pigments. Ability of natural colorant to be used as natural dyes has been known since ancient times. A dye can generally be described as “a colored substance that has an affinity to the substrate to which it is being applied”.

The art of dyeing was as old as human civilization. From the historical records, it is learnt that natural colorants were available to people during Greco-Roman periods. Then, in 1856 William Henry Perkin, an English chemist, while attempting to synthesize quinine from aniline, a coal tar byproduct, accidentally produced and discovered "mauve" the first synthetic dye. The color quickly became the favorite of royal family and a new industry was born-Dyestuff Industry. The advent of synthetic dyes and their immediate acceptability throughout the world due to wide range of colors and good color fastness properties resulted in the limited use of natural dyeing.

2. DYES

2.1. Dye definition

Dyes are intensely coloured substances used for the coloration of various substrates including paper, leather, fur, hair, foods, drugs, plastics and textile materials. They are retained in these substrates by physical adsorption, salt or metal complex formation or by the formation of covalent chemical bonds [9]. Until the middle of nineteenth century all dyes were natural products, extracted in most cases from a variety of plants, but also from a few animal sources. Plant sources include roots, stems, leaves, flowers and fruits while animal sources include certain dried insects. At present practically all dyes are coloured organic chemicals synthesized from products of the petro-chemical and coal-tar industries [10].

Unlike most organic compounds, dyes possess colour because they absorb light in the visible spectrum (400–700 nm), they have at least one chromophore (colour-bearing group), they have a conjugated system, and they exhibit resonance of electrons, which is a stabilizing force in organic compounds. When any one of these features is lacking from the molecular structure the colour is lost. In addition to chromophores, most dyes also contain groups known as auxochromes (colour helpers), examples of which are carboxylic acid, sulfonic acid, amino, and hydroxyl groups. While these are not responsible for colour, their presence can shift the colour of a colourant and they are most often used to influence dye solubility

2.2. Classification of dyes

Chemical structures determine the colors, properties and uses of dyes, and provide the only rational basis of a classification of these compounds. The categories of colorants recognized in the COLOUR INDEX and in the first nine editions of Conn are set out in Table 1.1.

Table 1.1. Constitution (chemical) classes of dyes recognized in the *Colour Index*.


Nitroso dyes	Indophenol dyes
Nitro dyes	Azine dyes
Azo dyes	Oxazine dyes
Azoic dyes	Thiazine dyes
Stilbene dyes	Sulfur dyes
Carotenoid dyes	Lactone dyes
Diphenylmethane dyes	Aminoketone dyes
Triarylmethane dyes	Hydroxyketone dyes
Xanthene dyes	Anthraquinone dyes
Acridine dyes	Indigoid dyes
Quinoline dyes	Phthalocyanine dyes
Methine dyes	Natural organic coloring matters
Thiazole dyes	Oxidation bases
Indamine dyes	Inorganic coloring matters

2.3. Specific interest to azo dyes


The azo group, $-N=N-$, is present in more commercially available dyes than any other chromophore. There are many applications in both industry and the laboratory for the dyes themselves and for the intermediate compounds that react with one another to form azo dyes or pigments.

This linkage may be present more than one time and thus mono azo dyes have one azo linkage while two in diazo and three in triazo respectively. These azo groups are connected on both sides with aromatics like benzene and naphthalene moiety. Sometimes aromatic heterocyclic units are also present being connected with azo groups [11]. Different shades of the same dye having various intensities of color are due to these aromatic side groups. Azo dyes containing sulfonate groups as substituent are called as sulphonated azo dyes. Azo groups in conjugation with aromatic substituents or enolizable groups make a complex structure which lead to huge expression of variation of colors in dyes [12,13].

Some common examples of azo dyes are shown in Figure 1.1.

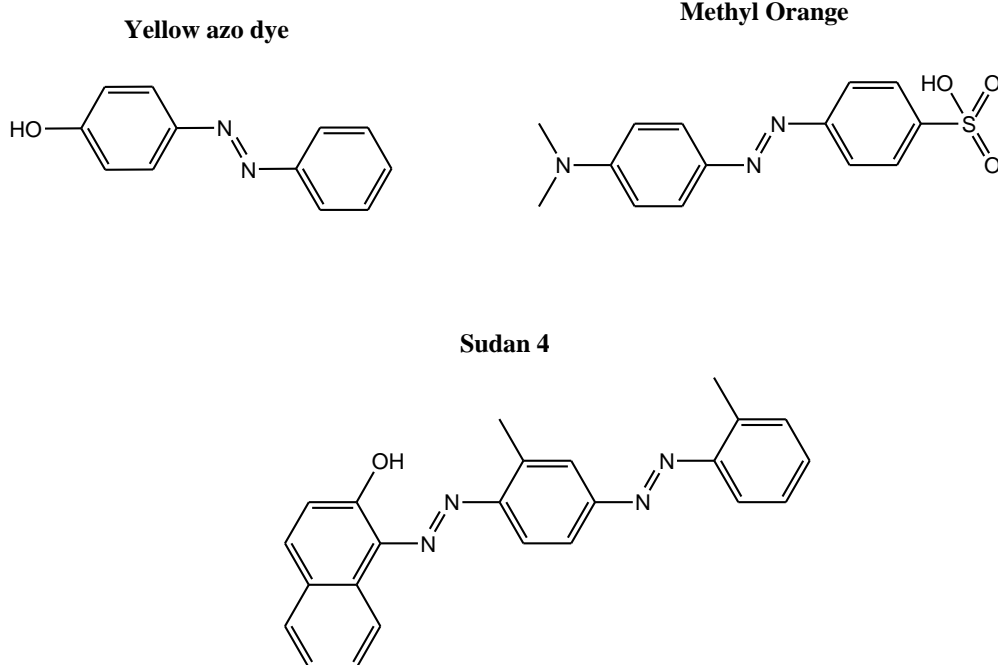


An azo group is formed when a diazonium ion, known as the diazo component, reacts with either phenol or an amine, known as the coupling component. Diazonium ions are generated by the reaction of nitrous acid (from NaNO_2 and HCl) on aromatic primary amines at about 0°C (Scheme 1.1).

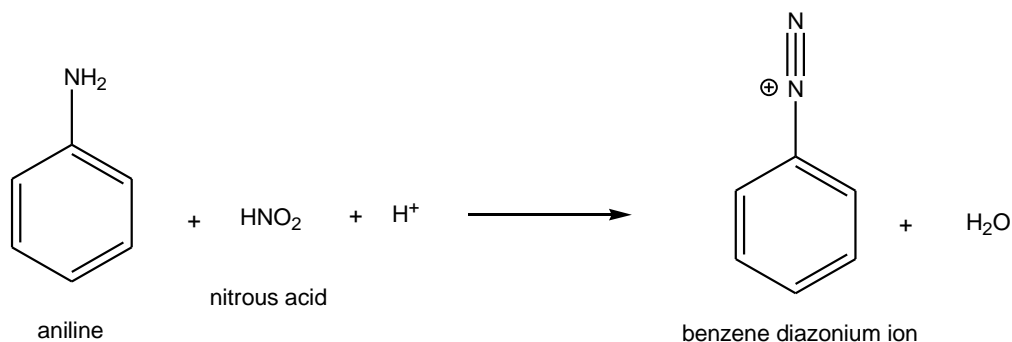

Scheme 1.1. Synthesis of benzene diazonium ion

Most diazonium salts are unstable, so they are used as soon as they have been made. In the azo coupling reaction, the end nitrogen atom of a diazonium ion displaces a hydrogen from the aromatic ring of phenol or amine. The coupling occurs *para* or *ortho* to the hydroxyl or amine group. The *para* position is favored if it is not already occupied or hindered by other substituents. For example, benzene diazonium chloride couples with dimethylaniline to form *p*-dimethylaminoazobenzene (Scheme 1.2.).

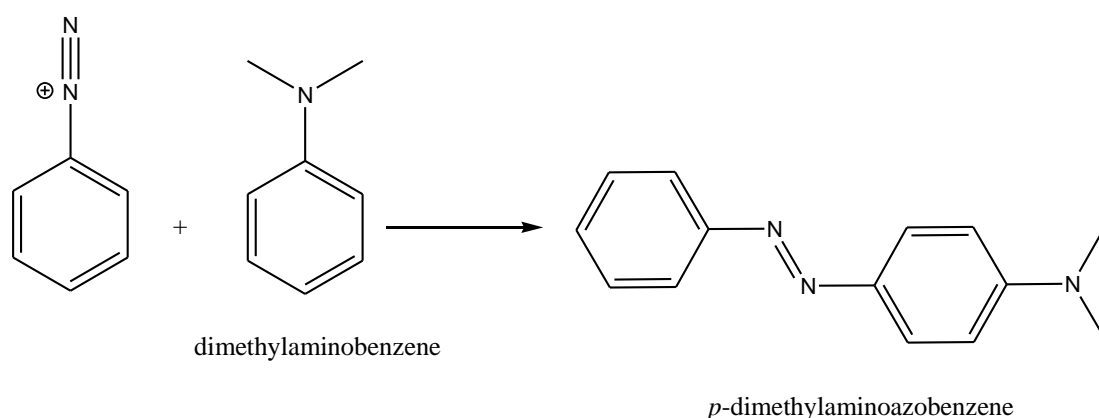

Scheme 1.2. Synthesis of *p*-dimethylaminoazobenzene

The diazotate ion cannot couple. The synthesis of the dye must therefore be carried out at a pH that is a compromise between the alkalinity needed to generate the coupling component and the acidity that preserves the diazonium ion. The optimal pH is different for every pair of

reactants; most phenols require more strongly alkaline conditions than most amines. Colored azo compounds can be synthesized by several methods other than coupling of diazonium salts [14], but such reactions are not often exploited commercially.

2.4. Classification of azo dyes

2.4.1. Cationic or basic azo dyes

These may have amine side chains, which are protonated in solutions at low pH, or quaternary nitrogen atoms, which are positively charged even under neutral or alkaline conditions. The charged group may be part of the chromogen (delocalized cationic dyes) or attached by a non conjugated chain of carbon atoms (pendant cationic dyes).

2.4.2 Anionic or acid azo dyes

These have sulfonic or carboxylic acid groups attached to their aromatic rings. Sulfonic acids are strong (ionized at any pH), so the colored ions are always negatively charged. In acidic media, they are attracted to protonated amino groups of protein fibers (wool, silk). A carboxylic acid may not be entirely ionized at the pH of the dye bath.

2.4.3. Direct azo dyes

These anionic dyes have large molecules (two or more azo linkages) that can assume a coplanar conformation. Direct dyes bind to cellulose (cotton, linen) by nonionic, non covalent forces.

2.4.4. Reactive azo dyes

These have pendant side chains that can combine covalently with the substrate. Attachment to the hydroxyl groups of cellulose is a major commercial application; the color has greater resistance to washing than can be obtained with any other type of dyeing.

2.4.5. Mordant azo dyes

In these, a hydroxyl group is adjacent to a ring carbon that is joined to either an azo nitrogen atom or a carboxyl group. Either arrangement can combine with a metal atom, such as chromium (III), to form a stable five- or six-membered chelate ring. The dye-metal complex can be bound firmly by various types of substrates.

3. DYEING

3.1. Definition

Dyeing is a process of colouring textile fibres and other materials so that colouring matter becomes an integral part of the material rather than a surface coating. The mechanism of dyeing must differ with the nature of the material, that is, whether it is protein, cellulose or some synthetic substance [15]. The appropriate dye class for the fibre must be used along with specific dyeing conditions in order to gain an optimum result [16].

4. WOOL

4.1. Structure and chemical composition of wool fibre

Wool is a complex natural fibre composed mainly of proteins (97%) and lipids (1%), with a heterogeneous morphological structure [17]. Wool fibres have approximately the form of elliptical cylinders, with average diameters ranging from 15 μm to 50 μm and lengths determined by the rate of growth of the wool and the frequency of shearing. Wool and other keratin fibres consist of two major morphological parts: the cuticle layer (usually referred to as scale layer of wool) which is composed of overlapping cells that surround the cortex (inner part of the fibre). The cortex comprises spindle-shaped cortex cells that are separated from each other by a cell-membrane complex (Figure 1.2), which consists of non-keratinous proteins and lipids [18].

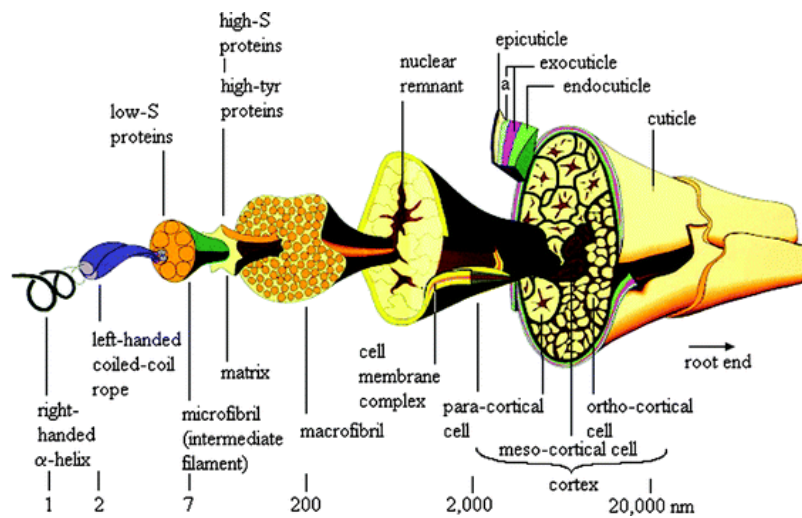


Figure 1.2 – Cross-section diagram of a merino wool fibre showing the structure at progressive magnifications.

The cuticle cells are laminar, rectangular structures which form a sheath of overlapping scales enveloping the cortex.

They comprise 10% of the total weight of the wool fibre. The cuticle cells are composed of three distinct layers. The outermost layer is the outer resistant surface membrane (epicuticle); the next layer from the surface of the cells is called the exocuticle, which is subdivided into two main layers (A and B-layers) that differ mainly in the cystine content. Finally the endocuticle is the cuticular layer nearest to the cortex [19].

The protein fiber wool consists of carbon, hydrogen, oxygen, nitrogen, and sulfur. The elemental analysis of wool is as follows:

Carbon	50.5 wt%
Hydrogen	6.8 wt%
Oxygen	22 wt%
Nitrogen	16.5 wt%
Sulfur	3.7 wt%
Ash	0.5 wt%

4.2. Chemical properties of wool fibre

4.2.1. Effect of acids

Concentrated acids damage it since they hydrolyze the salt linkages and hydrogen bonds. Dilute acids do not affect it.

4.2.2. Effect of alkali

It easily dissolves in alkaline solutions. Alkalis hydrolyze the disulphide bonds; hydrogen bonds and salt linkages of wool and cause the polymers to separate from each other, which is looked as dissolution of the fibre. Hydrolysis of the peptide bonds of wool polymers lead to polymer fragmentation and total destruction of the strand. Prolonged exposure to alkalis causes hydrolysis of the peptide bonds of wool polymers lead to polymer fragmentation and total destruction of the fibre.

4.2.3. Effect of bleach

Chlorine bleach is ordinary harmful to the wool. KMnO_4 , Na_2O_2 are utilized for bleaching.

5. International Commission on Illumination: Color Systems

The CIE, or “Commission Internationale de l’Eclairage” (translated as the International Commission on Illumination), is the body responsible for international recommendations for photometry and colorimetry. In 1931 the CIE standardized color order systems by specifying the light source (or illuminants), the observer and the methodology used to derive values for describing color. The CIE Color Systems utilize three coordinates to locate a color in a color space. These color spaces include:

- CIE $L^*a^*b^*$
- CIE $L^*C^*h^\circ$

To obtain these values, we must understand how they are calculated. As stated earlier, our eyes need three things to see color: a light source, an object and an observer/processor. The same must be true for instruments to see color. Color measurement instruments receive color the same way our eyes do—by gathering and filtering the wavelengths of light reflected from an object. The instrument perceives the reflected light wavelengths as numeric values. These

values are recorded as points across the visible spectrum and are called spectral data. Spectral data is represented as a spectral curve. This curve is the color's fingerprint.

Once we obtain a color's reflectance curve, we can apply mathematics to map the color onto a color space. To do this, we take the reflectance curve and multiply the data by a CIE standard illuminant. The illuminant is a graphical representation of the light source under which the samples are viewed. Each light source has a power distribution that affects how we see color. Examples of different illuminants are A — incandescent, D65 — daylight and F2 — fluorescent. We multiply the result of this calculation by the CIE standard observer. The CIE commissioned work in 1931 and 1964 to derive the concept of a standard observer, which is based on the average human response to wavelengths of light.

In short, the standard observer represents how an average person sees color across the visible spectrum. Once these values are calculated, we convert the data into the tristimulus values of XYZ. These values can now identify a color numerically.

5.1. CIELAB ($L^*a^*b^*$)

When a color is expressed in CIELAB, L^* defines lightness, a^* denotes the red/green value and b^* the yellow/blue value.

Figures 1.3 and 1.4 show the color-plotting diagrams for $L^*a^*b^*$. The a^* axis runs from left to right. A color measurement movement in the $+a$ direction depicts a shift toward red. Along the b^* axis, $+b$ movement represents a shift toward yellow. The center L^* axis shows $L = 0$ (black or total absorption) at the bottom.

At the center of this plane is neutral or gray.

To demonstrate how the $L^*a^*b^*$ values represent the specific colors of Flowers A and B, we've plotted their values on the CIELAB

Color Chart in Figure 1.3. The a^* and b^* values for Flowers A and B intersect at color spaces identified respectively as points A and B. These points specify each flower's hue (color) and chroma (vividness/dullness). When their L^* values (degree of lightness) are added in Figure 1.5, the final color of each flower is obtained.

5.2. CIELCH ($L^*C^*h^\circ$)

While CIELAB uses Cartesian coordinates to calculate a color in a color space, CIELCH uses polar coordinates. This color expression can be derived from CIELAB. The L^* defines lightness, C^* specifies chroma and h° denotes hue angle, an angular measurement.

5.3. Three-dimensional color system

Spectrophotometry's applications are seemingly boundless. Colormatching measurements are made every day by those comparing a reproduced object to a reference point. Spectrophotometry-assisted color measurement can be useful in areas such as:

- Corporate logo standardization
- Color testing of inks
- Color control of paints
- Control of printed colors on packaging material and labels
- Color control of plastics and textiles throughout the development and manufacturing process
- Finished products like printed cans, clothing, shoes, automobile components, plastic components of all types

Each color has its own distinct appearance, based on three elements: hue, chroma and value (lightness). By describing a color using these three attributes, you can accurately identify a particular color and distinguish it from any other.

5.3.1. Hue

When asked to identify the color of an object, you'll most likely speak first of its hue. Quite simply, hue is how we perceive an object's color — red, orange, green, blue, etc. The color wheel in Figure 1.3 shows the continuum of color from one hue to the next. As the wheel illustrates, if you were to mix blue and green paints, you would get blue green. Add yellow to green for yellow-green, and so on.

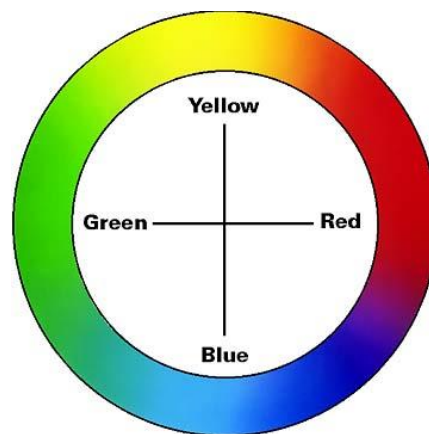


Figure 1.3. Hue

5.3.2. Chroma

Chroma describes the vividness or dullness of a color — in other words, how close the color is to either gray or the pure hue. For example, think of the appearance of a tomato and a radish. The red of the tomato is vivid, while the radish appears duller.

Figure 1.4 shows how chroma changes as we move from center to the perimeter. Colors in the center are gray (dull) and become more saturated (vivid) as they move toward the perimeter. Chroma also is known as saturation.

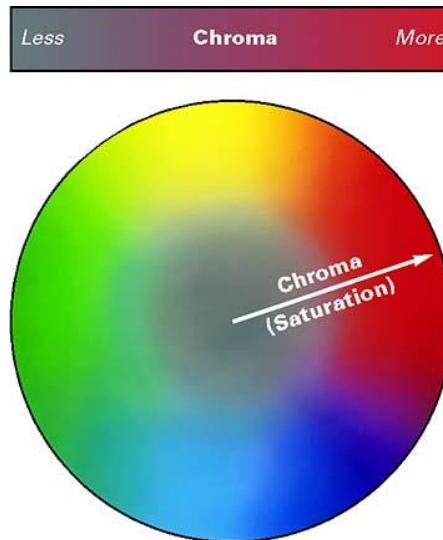


Figure 1.4. Chromaticity

5.3.3. Lightness

The luminous intensity of a color — i.e., its degree of lightness — is called its value. Colors can be classified as light or dark when comparing their value.

For example, when a tomato and a radish are placed side by side, the red of the tomato appears to be much lighter. In contrast, the radish has a darker red value. In Figure 1.5, the value, or lightness, characteristic is represented on the vertical axis.

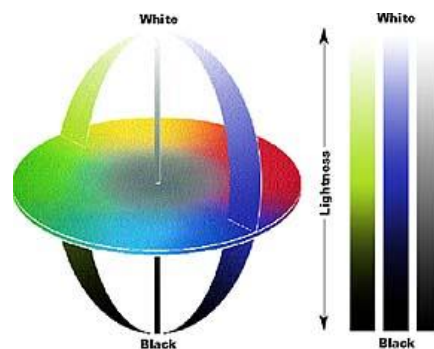


Figure 1.5. Three-dimensional color system depicting lightness

CHAPTER 2

Materials and Methods

1. Materials

1.1. Chemicals

1-Amino-4-methyl-naphthalen-2-ol, Sodium nitrite, *p*-nitro-aniline, hydrochloric acid, sulphamic acid and riboflavin were obtained from Sigma Aldrich (St Louis, MO, USA).

1.2. Proton NMR Spectrometer

NMR spectra were obtained on a Bruker AC 300 spectrometer operating at 300 MHz for ¹H. Chemical shifts are given in parts per million relative to tetramethylsilane (TMS) and the coupling constants *J* are given in Hertz. The spectrum was recorded in DMSO as solvent at room temperature.

1.3. Infrared spectrometer

IR spectra were recorded on a Perkin-Elmer IR-197 spectrometer

1.4. Wool fabrics

The used wool was a scoured and bleached wool fabric of 205 g/m², 72 ends per inch and 64 picks per inch.

1.5. Dyeing materials

Preliminary dyeing test have developed in the montage presented in figure 2.1. Before testing the overall fastness properties, dyeing test have been assisted in an Ahiba nuance top speed, shown in figure 2.2.



Figure 2.1 : Montage of preliminary dyeing experiments



Figure 2.2: AHIBA nuance Top speed II

The Ahiba is a state of dyeing fiber fabrics. It addresses a wide range of dyeing and testing requirements at an affordable price. The unit produces accurate laboratory sample dyeing with the levelness and reproducibility. The Ahiba can accommodate many different beaker sizes and quantities maximizing the versatility of the machine.

1.6. Equipment of Colour strength and colour depth measurements

The colour yield of samples was evaluated by light reflectance measurements using SF 300 spectrophotometer. Relative colour strengths (K/S values) were determined using the Kubelka-Munk equation [20]:

$$K/S = (1 - R^2) / 2R$$



Figure 2.3 : SF 300 spectrophotometer

1.7. Equipment of Rubbing Fastness test

Crockmeter/Rubbing Fastness is used to determine the colour fastness of textiles to dry or wet rubbing.



Figure 2.4 : Crockmeter

1.8. Equipment of washing Fastness test

Autowash machine was used to determine the dye fastness propriety to washing.



Figure 2.5 : Autowash machine

1.9. Equipement of testing the light Fastness propriety

Suntest SPC Plus ATLAS is a machine used for determining the strength of the test light. It is equipped with a xenon lamp.



Figure 2.6 : Suntest SPC Plus ATLAS

2. Methods

2.1. Synthesis of azo dye

A solution of sodium nitrite (NaNO_2 , 0.058 mol), in water (20 mL), was added slowly to a mixture of *p*-nitro-aniline (0.05 mol), in water (20 mL) and hydrochloric acid (30%, 0.125 mol), at 0-5 °C. After 30 min at 0-5 °C and pH less than 2, excess nitrous acid was destroyed by adding sulphamic acid. The resulting solution of benzene diazonium chloride was added slowly to a solution of 1-amino-4-methyl-naphthalen-2-ol (0.05 mol), at pH 6-6.5. The mixture was stirred for 30 min at room temperature and at pH 6.5. The solid product (1-amino-4-methyl-3-(4-nitro-phenylazo)-naphthalen-2-ol) was collected and purified by dissolving in distilled water (100 mL) and re-precipitating by slow addition of potassium chloride (30% w/v) to the stirred solution [21].

2.2. Wool pre-treatment

Before dyeing, wool fabric was further treated with a solution containing 5 g/L of sodium carbonate and 3 g/L of non-ionic detergent (Hostapal CV, Clariant), at 50 °C for 30 min. Then, it was thoroughly rinsed and air dried at room temperature.

2.3. Dyeing procedure

In a dye bath containing different amounts of dye (0.25-1.5 g/L) with liquor ratio 40:1, wool fabric was dyed using conventional heating (CH) at different pH values (3,5,7,9,11) for 30 minutes and at different temperatures (60-90 °C). The dyed samples were rinsed with cold water and finally dried at ambient temperature. The pH values were recorded with Hanna pH meter, the dye bath was acidic (pH 5). To work at pH values superiors at 5, the pH values were adjusted with dilute solutions of sodium carbonate and to work at pH values inferiors at 5, the pH values were adjusted with dilute solutions of hydrochloric acid [22].

2.4. Colour fastness test


The dyed samples were tested for fastness properties according to standard methods, the specific tests were for colour fastness to washing ISO 105-C02:1989, colour fastness to rubbing ISO 105-X12:1987, colour fastness to water ISO 105-E01:1989 and colour fastness to light ISO 105-B02:1988 (carbon arc).

CHAPTER 3

Results and discussion

1. Synthesis and ^1H NMR study of azo dye 3

The synthesis of azo-dye **3** is produced in two step. The first step is the formation of aromatic diazonium cation and the second step is the coupling reaction between this cation and 1-amino-4-methyl-naphthalen-2-ol **1** (Scheme 3.1).

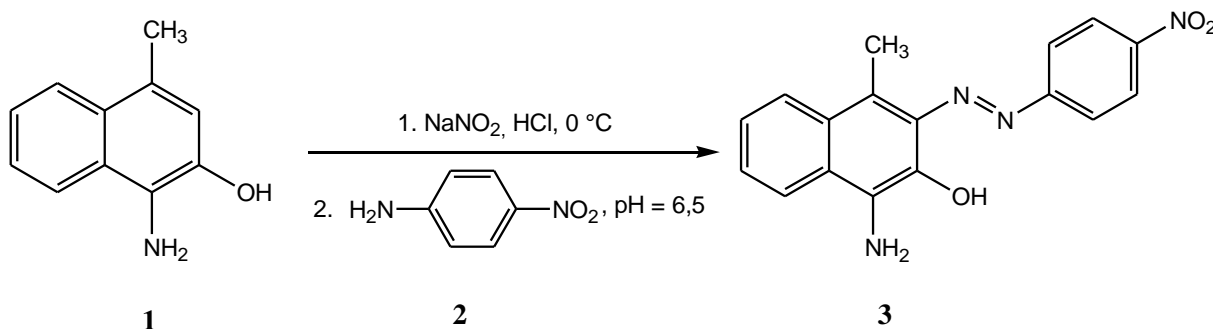

Scheme 3.1. Synthesis of azo dye **3**

1.1. Structural study of azo dyes **3**

A structure of a new compound **3** has been elucidated by FT-IR and ^1H -NMR measurements. Concerning the IR spectra of the azo dye **3**, structure was confirmed by functional group identification. Amino and alcohol group gave its peak at 3269 cm^{-1} , and appearance of the weak absorption band at 1548 cm^{-1} was due to the stretching band of azo group (Figure 3.1).

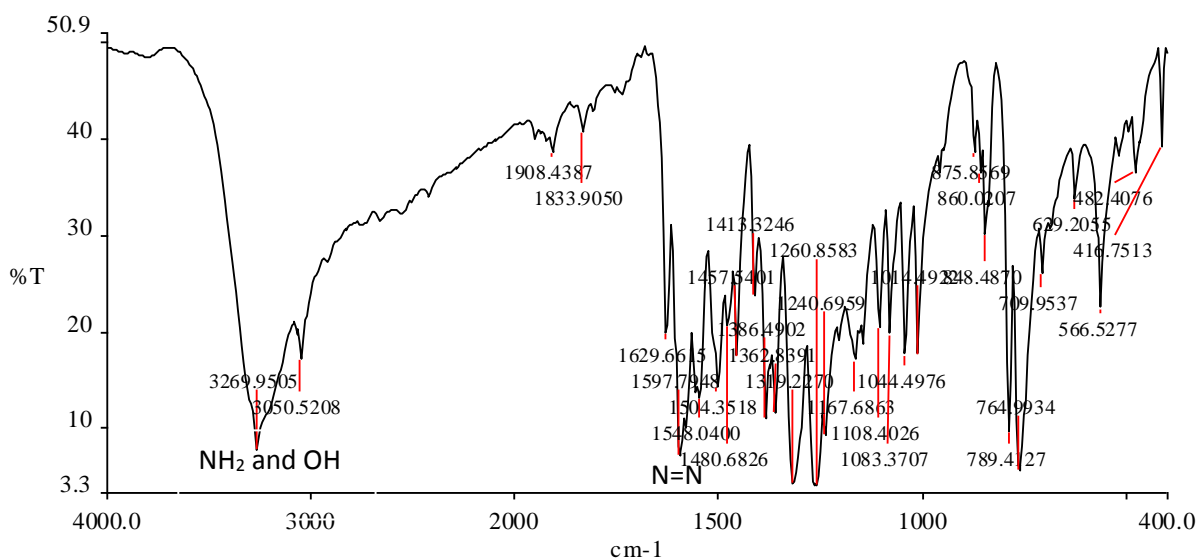


Figure 3.1 IR spectra of azo dye **3**

^1H NMR of azo dye **3** is recorded in DMSO. Dye show singlet at 2.37 ppm, which can be attributed to the methylene proton of phenyl ring. The aromatic protons are observed at 7.24-8.03 ppm, the four hydrogen atoms attached to the *para*-disubstituted ring gave an AA'BB' spin system. Compound **3** showed two broad absorptions as singlets at 10.05 ppm and 11.67 ppm, these confirmed the presence of NH_2 and OH groups (Figure 3.2).

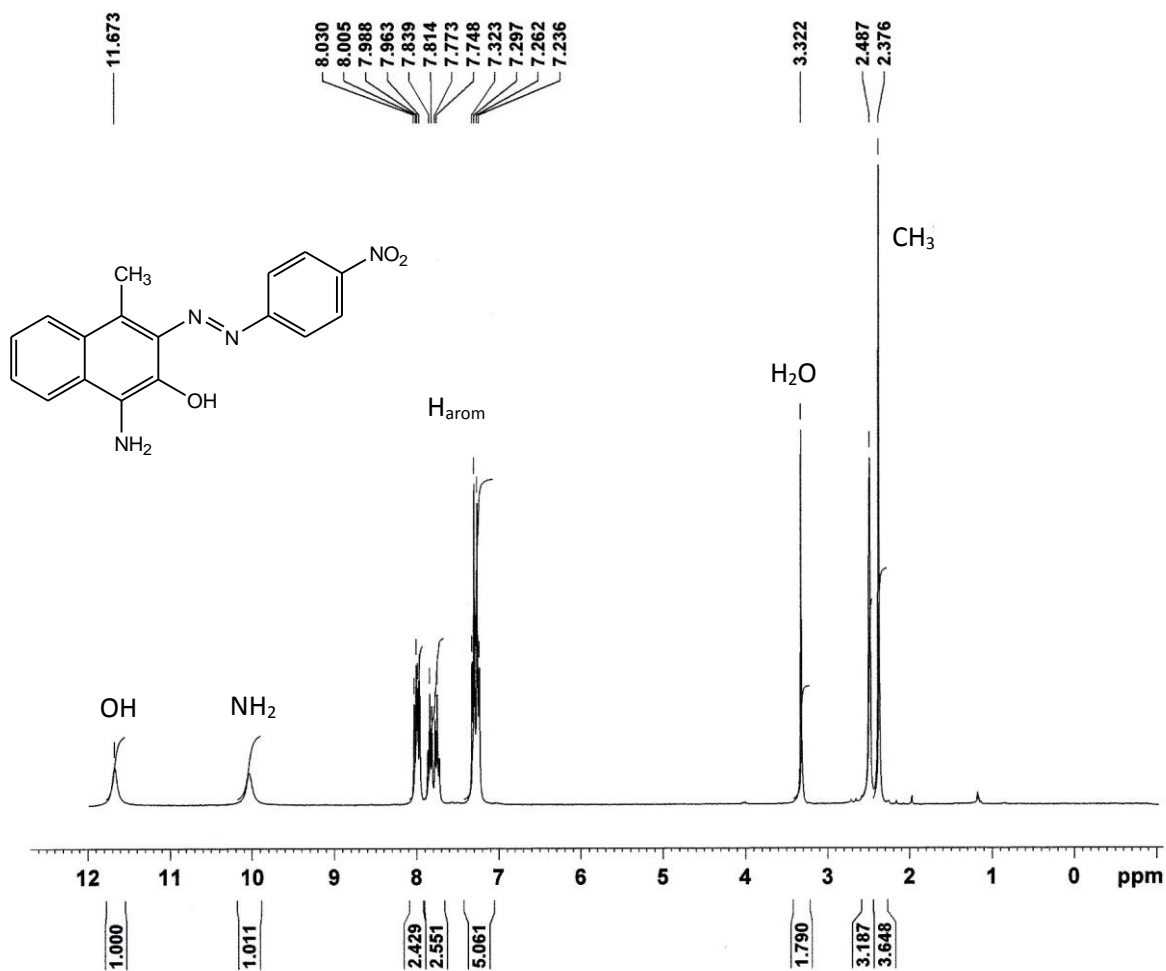


Figure 3.2. ^1H NMR spectra of azo dye **3**

2. Dyeing of wool fabrics with azo dye

Wool fabrics were dyed with azo dye at a liquor ratio of 40:1. The fabric was rinsed in tap water and air dried.

2.1. Effect of azo dye concentration on the dyeing of wool fabrics

The effect of dye concentration on the color strength (K/S) of the dyed fabric has also been investigated. It was found that color strength of the fabric increases with increasing the concentration of the dye (**Table 3.1**). However, the rate of increase of color strength decreases with the increase in the concentration of the dye above 0.5 mol.L⁻¹, after which the fibres started to become saturated and aggregation phenomena of dyes in the dye bath can be produced.

Table 3.1. Color values of azo dye on wool: Effect of concentration

Dyeing conditions: pH 3, 30 min, 60 °C

C_{molL⁻¹}	L*	a*	b*	c*	h	K/S
0.25	45.90	36.10	30.51	47.24	40.21	9.24
<u>0.5</u>	<u>32.84</u>	<u>47.56</u>	<u>26.54</u>	<u>54.47</u>	<u>28.89</u>	<u>24.41</u>
1	51.53	29.70	20.55	36.12	34.68	9.40
1.5	36.40	10.20	11.31	14.15	30.06	6.13

2.2. Effect of pH on the dyeing of wool fabrics

Table 3.2 shows that the pH values of the dye bath have considerable effect on the dyeability of wool fabric with azo dye. The effect of dye bath pH can be attributed to the correlation between dye structure, the fibre used. The colour strength obtained was increased as the pH increases up 5, and then it decreases. Since the lac dye used is a water soluble dye containing hydroxyl and amino groups, it would interact ionically with the protonated terminal amino groups of wool fibres at acidic pH via ion exchange reaction. The weak hydroxylate anion of the dye that may be present at low pH replaces that of alcohol due to its higher affinity.

At $\text{pH} > 5$, however, the ionic interaction between the hydroxylate anion of the dye and wool fibres decreases due to decreasing number of protonated terminal amino groups of wool fibres and thus lowering its dyeability ($\text{pH} > \text{pH}_{\text{iso wool}} = 4.8$) (Qing et al., 2007).

At pH 5, the number of the protonated terminal amino groups of wool fibres becomes constant and no additional dye is adsorbed, the maximum colour strength was obtained at this value.

Table 3.2. Color values of azo dye on wool: Effect of pH

Dyeing conditions: C 0.5, 30 min 60 °C

pH	L*	a*	b*	c*	h	K/S
3	32.84	47.56	26.54	54.47	28.89	24.41
5	<u>26.65</u>	<u>48.51</u>	<u>27.51</u>	<u>53.23</u>	<u>26.87</u>	<u>28.31</u>
7	40.25	34.61	28.55	46.14	34.68	11.30
9	46.36	20.22	29.51	44.19	30.33	5.45
11	50.43	30.03	30.15	40.16	33.77	3.32

2.3. Effect of dyeing temperature

The effect of temperature on the dyeability of wool fabrics with azo dye was conducted at different temperatures (60, 70, 80, 90 °C). As shown in table 3.3, it is clear that the colour

strength increases with the dyeing temperature with a pronounced manner up 70 °C, later until 80 °C, the K/S values increase slowly, at 80°C or above a plateau value of K/S was observed.

Table 3.3 Color values of azo dye on wool: Effect of dyeing temperature

Dyeing conditions: C 0.5, 30 min

T(°C)	L*	a*	b*	c*	h	K/S
60	<u>26.65</u>	<u>48.51</u>	<u>27.51</u>	<u>53.23</u>	<u>26.87</u>	<u>28.31</u>
70	25.47	49.45	26.50	55.31	25.66	31.32
80	<u>41.55</u>	<u>33.89</u>	<u>27.46</u>	<u>46.33</u>	<u>35.66</u>	<u>32.36</u>
90	42.24	35.63	29.56	45.14	36.38	15.31

3. Colorimetric analysis of the dyed fabric

The values of color coordinates suggested that the color hue of the synthesized dye shifted toward the redder direction on the red-green axis as well as toward the yellowish direction on yellow-blue axis as positive values of a* and b* respectively.

4. Fastness properties of the dye on wool fabrics

Fastness properties of dyed wool fabric was studied and tabulated in table 3.4.

Table 3.4. Fastness properties of acid azo dye on wool fabric.

Dry rubbing fastness	Wet rubbing fastness	washing fastness	water fastness	light fastness
5	5	4-5	4-5	6

It was shown that dyed fabrics show a very good light and wash fastness properties.

Conclusion

New azo dye was synthesized and evaluated in dyeing wool fabric.

The structure of the synthesized compound was characterized using IR and ¹H-NMR spectroscopy.

Optimum conditions for the fixation of azo dye to the wool fabric were determined from the colour strength values on the dyed fabric.

The optimal conditions for dyeing wool fabrics with azo dye were carried out at 50 °C for 45 min at pH 5.

The synthesized dye showed good fastness to light, and very good fastness to washing and rubbing.

References

1. H. Zollinger, Color chemistry, Weinheim: WileyVCH, 2003.
2. P. F. Gordon, P. Gregory, Organic chemistry in color, New York: Springer-Verlag, 1983.
3. S. Waheed, C.M. Ashrat, Synthesis and Studies of Some Acid Dyes, Jour. Chem. Soc. Pak., 22, 2000, 49-53.
5. M.A. Zayed, G.G. Mohamed, S. A. M. Abdullah, Synthesis, structure investigation, spectral characteristics and biological activities of some novel azodyes, Spectrochim. Acta Part A, 78, 2011, 1027-1036.
6. M.H. Patel, Synthesis, Characterization and Dyeing Assessment of Novel Bisazo-Acid Dyes Derived from 2-hydroxy-4-Methoxybenzophenone-5-sulphonic acid, Int. J. Sci. Eng. Res., 5, 2014, 2213-2217.
7. Weaver MA, Shuttleworth L. Heterocyclic diazo component. Dyes Pigments 1982; 3:81-121.
8. Towns AD. Developments in azo disperse dyes derived from heterocyclic diazo components. Dyes Pigments 1999; 42:3-28.
9. Shah, K. M. *Handbook of synthetic dyes and pigments*, 2nd edition, Multi-tech publishing co., India, **1998**, Vol. 1: Synthetic dyes, pp 3.
10. Duff, D. G.; Sinclair, R. S. *Giles's Laboratory course in dyeing*, 4th edition, Society of Dyers and Colourists: England, **1989**.
11. Zollinger, H.,. *Color Chemistry-Synthesis, Properties and Application of Organic Dyes and Pigments*, VCH publishers, New York, 1987, 92-102.
12. Gaspar B, Hills B, Dreyfuss PD, Nuys V. Acid azo dyes. US 2612496, 1948.
13. Bornengo G, Merlo F, Paffoni C. Water-soluble acid azo dye. US 4187218, 1980.
14. Stohr B, Nickel, H. Piperazinyl-triazinyl naphtholsulphonic acid azo dyes. US 4544737, 1985.
15. Noller, C. R. *Chemistry of organic compounds*, 2nd edition, W. B. Saunders Company: London, **1957**, pp 673.
16. Welham, A. The theory of dyeing and the secret of life, *J.S.D.C.* **2000**, 116, 141.
17. Araújo M, Melo e Castro EM (1984). In: *Manual de Engenharia Têxtil*, Fundação Calouste Gulbenkian, Vol. II, Lisbon.

18. Fact Sheet (2005). *Characteristics of wool*, Division American Sheep Industry Association, Inc. (www.sheepusa.org), 2 p.
19. Negri AP, Cornell HJ, Rivett DE (1993). A model for the surface of keratin fibers. *Textile Research Journal* 63(2): 109-115.
20. Judd, D.B., Wysezcki, G., 1975. *Colour in Business, Science and Industry*, John Wiley & Sons, New York, NY, USA, 3rd edition.
21. Divyesh R. Patel, Keshav C. Patel *Dyes and Pigments* 90 2011 1-10.
22. Guesmi, A.; Ben Hamadi, N.; Ladhari, N.; Sakli, F.; *Ind. Crop. Prod.* 2013, 42,63-69.
23. Qing, L.P., Rex, B., Xungai, W., 2007. Influence of pH on hygral expansion, relaxation shrinkage and extensibility of wool fabric. *Fibers Polym.* 8, 230–233.

الخلاصة

تم تحضير صبغه جديده (صبغة الازو) من حلقة الامين تحتوي على 1-امين-4-ميثيل-نفتالين-2-ال بالتديير واقتران التفاعل . هذه الصبغه اتسمت باستخدام جهاز الاشعه تحت الحمراء , وجهاز الطنين النووي المغناطيسي . تم تقييم صبغ الصبغه على الصوف واتضح ثبات الضوء جيد جدا والثباتيه بعد الغسيل وثباتيت خصائص الفك , وقد تم التحقق من الخواص الطيفيه والبيانات اللونيه

(L*, a*, b*, C*, h*, K/S)

استخدام نهج جديد لصبغ عملية نسيج الصوف مع الأصباغ عديمة الأحياء: عملية التنمية والتحسين

قدم هذا البحث من متطلبات الحصول على درجة البكلوريوس في الكيمياء

قسم الكيمياء (كيمياء عامه)

كلية العلوم

جامعة الامام محمد بن سعود الاسلاميه

أعداد الطالب

فهد بن محمد القحطاني

